



Synthesis and Study of Microcrystalline Parameters with Electrical Conductivity of Al Doped Lithium Ferrites

SURESH. S. DAROKAR

Science College, Congress Nagar, Nagpur-12, Maharashtra, India.

Abstract

Magnetoplumbite type of lithium ferrites substituted by aluminium ions having general chemical formula $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ (where $x = 1$ to 6) were prepared by standard solid state reaction method. The compounds are in single hexagonal phase without traces of uncertainly ambiguous reflection. From XRD pattern lattice parameters has recorded with increasing doped aluminium element in the range from $a = 5.807 \text{ \AA}$ to $5.906 \text{ \AA}$ and $c = 22.507 \text{ \AA}$ to $22.585 \text{ \AA}$ pertaining the space group $P6_3/\text{mmc}$ (No.194). The mass density of the ferrites were found linearly varies and depends upon the mass and volume of sample. The X-Ray density has depends upon the lattice constant and molecular weight of the compounds. The average particle size was also estimated. Electrical properties such as dc conductivity, activation energy were studied. Also, the type of carriers responsible in each was determined from thermoelectric studies. The higher resistivity of the compounds $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ suggests less presence of mixed valency cations on equivalent lattice. While Fe show low value due to the ferrous ions present on the octahedral sites along with ferric ions.



Article History

Received: 07 November 2017

Accepted: 17 November 2017

Keywords:

Lithium ferrite,
Electrical
Conductivity,
Activation
energy etc.

Introduction

A recent literature survey of magnetoplumbite revealed that the electrical properties of hexagonal¹⁻⁴ ferrites are less studied compared to its electrical and magnetic properties. This may be due to the fact that they were developed initially as permanent magnet⁵⁻⁸. Today M-type ferrites are finding applications in many diverse fields like

microwave and hence their electrical properties are also becoming important. Many attempts have been made to improve the properties of M ferrites by variety of substitutions. Though M-type ferrite does not contain any monovalent cation, hence a combination of monovalent cation with some multivalent cation for charge compensation may be substituted. With this idea, a new series of

CONTACT Suresh. S. Darokar ✉ sureshdarokar@gmail.com 📍 Science College, Congress Nagar, Nagpur-12, Maharashtra, India.

© 2017 The Author(s). Published by Oriental Scientific Publishing Company.

This is an Open Access article licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 4.0 International License (<https://creativecommons.org/licenses/by-nc-sa/4.0/>), which permits unrestricted NonCommercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

To Link to this Article: <http://dx.doi.org/10.13005/msri/140216>

materials for permanent magnets of Ba-ferrites were developed for the first time⁹⁻¹⁰. Since the properties of ferrite depend on the interactions among the cations distributed over various sites, these were explained on the basis of the knowledge of site distribution of cations in the magnetoplumbite structure. In the present work M-type ferrites having common formula $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ were prepared and their electrical properties such as conductivity, activation energy and thermoelectric power were studied

Materials and Methods

In present investigation the series of M-type compounds, in were prepared using the standard solid-state reaction method^{11,12} using AR grade oxides as starting materials. Preparation of ferrites from Hexagonal family are usually difficult as compared to Spinel ferrites and especially the M-type ferrite is one of the most difficult one. This is due to the higher formation temperature and difficulty to get a pure product. The prolonged and continuous heating (1200 °C sintering temperature maintained for about 120 hours) used in present work resulted in better product formation as this has given sufficient time to the ions to diffuse. Also the lithium present, in these compounds might have facilitated the synthesis.

In present work, X-ray diffractometer with filtered Cu K α radiation from X-ray tube, operating at 40 KV and 20 mA were used for identification of compounds. (Philipse PW 1710). From the X-ray graph, formation of hexagonal structure, corresponding to space group P₆³/mmc or D₆⁴h (No 194) was checked.

Two-terminal method was employed for measurement of dc electrical conductivity. The measurements were taken in the range from 150 °C to 700 °C. Finally graphs of $\ln \sigma$ against $1/T$ were plotted and from the slope of these graphs the activation energies for the compounds were calculated using the relation,

$$\Delta E = 8.617 \times 10^{-5} [\Delta(\ln(1/\sigma)) / \Delta(1/T)]$$

The See back coefficient measurements were carried out using two-probe set up fabricated in the laboratory. The measurements were taken in the temperature range 350 °K to 450 °K. The type of carriers responsible for conduction was determined in each of the compound from the se studies. In

order to prepare pellet for the above observations the compound prepared was grounded to fine particle size in anagate mortar. The powder was mixed with 5% polyvinyl acetate solution made in A.R. grade acetone, as binder and mixed thoroughly. This mass was then transferred to a die and pressed under pressure of 5 tons per cm² using ahydraulic press. The pellets so prepared were then heated in a furnace up to 500 °C to remove the binder. After maintaining this temperature for few hours the pellets were slowly cooled to room temperature. In this way crack free pellets in the shape of a cylinder of small height were obtained. The end faces of the pellets, so prepared, were gently grounded over zero number sand paper to ensure smooth surfaces. The dimensions of the pellets were measured accurately. The smooth and flat parallel faces of the pellets were coated with uniform thin layer of silver paste to facilitate a good electrical contact with the electrodes. The silver paste was dried by heating the pellet slowly for few hours in air at 500 °C. The thin coating of silver paste thus formed was adherent and chemically inert. Pellets were stored in desiccators if found necessary.

Results and Discussion

The consolidated data of lattice parameters, Molecular weights and X-ray densities derived from the X-ray diffraction study, for the compounds studied in the present work, are given in table no.1. The formation of predominant M phase in all the compounds was confirmed from the X-ray study (figure No. 1).

All the compounds were prepared in polycrystalline form using stoichiometric mixtures of oxides with standard ceramic technique. The phase unicity of the samples were verified by using X-ray diffraction technique. The hexagonal lattice parameters of the compounds were deduced from XRD-pattern. The structural data viz. d_{observed} and $d_{\text{calculated}}$ and intensity observed with reflection hk lindices and the patterns are shown in figure-1. The crystallographic analysis of the samples shows single phase with magneto plumbite structure. The variation of lattice parameters and cell volume decreases linearly with increase in Al⁺³ and Fe⁺³ concentrations. The decrease in lattice parameters and cell volume agree well with the results of Haneda and Kojima¹¹ for the Ba-ferrites. In M-ferrites, in which the Fe⁺³ ions occupy

five crystallographic sites viz 2a, 2b, 4f_i, 4f₂ and 12k Lipka *et.al.*, (1990)¹². The magnetic behavior of the compounds has been explained, mainly due to

the interactions amongst the ions occupying these five sites. Due to several possible site distributions, various comparative magnetic interactions can arise

Table 1: Structural data of lithium hexaferrites Consolidated XRD data of $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ (x = 2, 3, 4, 5 & 6)

Compounds	a (A.U.)	c (A.U.)	Mol. Wt in gm	X-ray density gm/cm ³
$\text{Li}_{0.5}\text{Fe}_{2.5}\text{Al}_{10}\text{O}_{19}$	5.8594	22.3234	780.89	3.9065
$\text{Li}_{0.5}\text{Fe}_{3.5}\text{Al}_9\text{O}_{19}$	5.8181	21.8796	841.79	4.3578
$\text{Li}_{0.5}\text{Fe}_{4.5}\text{Al}_8\text{O}_{19}$	5.8076	21.8411	902.66	4.6992
$\text{Li}_{0.5}\text{Fe}_{5.5}\text{Al}_7\text{O}_{19}$	5.7948	21.8077	963.54	5.0473
$\text{Li}_{0.5}\text{Fe}_{6.5}\text{Al}_6\text{O}_{19}$	5.6953	21.2626	1024.4	5.6963

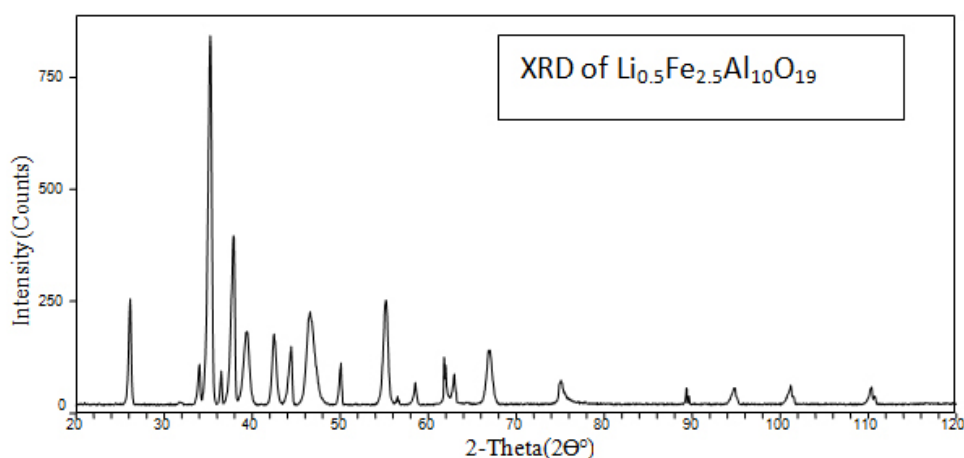


Fig. 1: X-ray diffraction of $\text{Li}_{0.5}\text{Fe}_{2.5}\text{Al}_{10}\text{O}_{19}$

in the lattice and in turn all these decides magnetic properties.

The results of dc electrical conductivity study are shown in the form of plots of conductivity $\ln \sigma$ against inverse absolute temperature. Variation of activation energy, electrical resistivity and electrical conductivity with Al ions in lithium ferrite is shown in figure no. 2. and compiled in the Table No 2. It was observed that the conductivity increases with temperature in all compounds and follows Wilson's law

$$\sigma = \sigma_0 \exp(\Delta E/kT)$$

This indicates semi-conducting nature of the compounds. The large values of resistivity and

activation energy are attributed to the relatively low number of mixed valency state of an element on an equivalent lattice sites. The increase in conductivity with temperature is attributed to the greater overlap of orbital due to the increased lattice vibrations. Since the overall distances get reduced during overlap, there is a greater probability of exchange of charges between the two overlapping ions. This increased exchange might have led to increase the conduction in the compound¹³.

The various divalent cations may be categorized as per their atomic radii, masses, magnetic nature and most importantly their site preferences. The exchange interactions responsible for conduction

mechanism depends on the overlapping of orbits and hence on actual locations of cations. Therefore the site distribution of these cations on various sites influences the conduction process and hence decides the conductivity of a M-type ferrite. As a result the conduction properties of the compounds prepared in the present work could be explained on the basis of distribution of cations.

The electrical properties of the $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ M type ferrite has been explained on the basis of the hopping of electrons in between the ferrous and

ferric cations ($\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$) present on the octahedral sites. The small quantity of Li, though occupies some of the octahedral sites, there is enough space on these sites for the iron cations. It has been revealed from the Mossbauer and other studies that the divalent Fe^{2+} cations locate on the octahedral sites of S-block^{14,15}. Due to this, iron cations of mixed valency on the octahedral sites are developed, which facilitated the electrical conduction. The lowest value of room temperature resistivity for this compound, among all the compounds studied in present work, could be attributed to this phenomenon. It can be

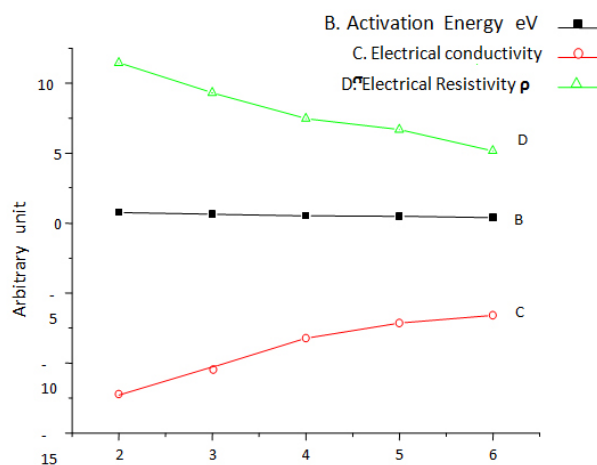


Fig. 2: Composition of Al Ions in Lithium ferrites $\text{Li}_{0.5}\text{Fe}_{0.5+x}\text{Al}_{12-x}\text{O}_{19}$ ($x=2,3,4,5,6$)

Table 2: Electrical Conductivity and activation energy of Li- Al ferrites

Compounds	Resistivity ρ at room Temp. ohms cm	Activation Energy ΔE (ev)	Conductivity σ at room temp ohms ⁻¹ cm ⁻¹
$\text{Li}_{0.5}\text{Fe}_{2.5}\text{Al}_{10}\text{O}_{19}$	4.08×10^{11}	0.73	2.447×10^{-11}
$\text{Li}_{0.5}\text{Fe}_{3.5}\text{Al}_9\text{O}_{19}$	8.21×10^8	0.60	1.218×10^{-11}
$\text{Li}_{0.5}\text{Fe}_{4.5}\text{Al}_8\text{O}_{19}$	6.21×10^8	0.57	1.631×10^{-9}
$\text{Li}_{0.5}\text{Fe}_{5.5}\text{Al}_7\text{O}_{19}$	2.38×10^7	0.50	4.196×10^{-8}
$\text{Li}_{0.5}\text{Fe}_{6.5}\text{Al}_6\text{O}_{19}$	2.147×10^6	0.45	4.656×10^{-7}

seen that the conductivity value obtained for the compounds in the present investigation is $2.447 \times 10^{-11} \text{ohm}^{-1} \text{cm}^{-1}$ to $4.656 \times 10^{-7} \text{ohm}^{-1} \text{cm}^{-1}$. There values of the conductivity may be partly attributed to the low evaporation of lithium from the samples prepared.

Conclusion

The formations of compounds were tested by XRD technique. The replacement of Fe^{+3} ions by Al^{+3} ions has been investigated because of resemblance of the ionic radii. It is seen that the former ions

are very easily replace at any substitution ratio without changing the crystal geometry. The lattice parameter a and c decrease linearly with substitution ratio in all compounds. The numerical value of the compositional data such as lattice constant, cell volume and X-ray density are reported and same nature in BaM and Sr M-ferrite.

The dc electrical conductivity of all the compounds has been calculated from the resistivity measurements from room temperature to 850 °K. The consolidated results of the room temperature resistivity and activation energies ΔE (eV) of all the compounds are determined. The resistivity of the compounds show low value due to the ferrous ions present on the octahedral sites along with ferric ions and as a result the conduction takes place in the form of hopping of electron from ferrous to ferric ion. The variation of resistivity in these compounds can be explained

on the basis of Verway mechanism¹⁶. Where the conduction is due to the electron exchange between ions Fe^{+3} and Fe^{+2} of the same element, present in more than one valence state. The unreacted impurities probably contain same Fe^{+2} ions which have migrated in growing particles of ferrite (Fe^{+3} species) subjected to proper sintering of samples. The concentrations of Fe^{+2} ions so produced is negligibly small which were not detected.

Aknowledgement

The author is thankful to UGC New Delhi for providing financial assistance to carry out this work under minor research project scheme File No.47-1345/10(WRO). Author also thankful to Dr. N.S. Bhavé, Dr. D.K. Burghate, Dr. D.K. Kulkarni, Dr.J.M. Khobragade and Dr.S.B. Khasare to guided and allowed laboratory facilities to work out this series of M-type hexaferrites.

References

1. J.Beretea and T.Brown. *Austral.J.Chem.* 24(1971) 273
2. G. Albanese, A Deriu, E. Luchini and G. Slokar. *Appl Phys A* 2(1981) 45
3. B.X.Gu, H.Y.Zang, H.R. Zhai, B.G. Slen, M.Lu, S.Y. Zhang and Y.Z. Maoi, *J Phys State Sol* 133 (1992) K83
4. Hanmawalt (1936) International table for X-ray diffraction photograph
5. X.Obrador, A Isalgue, A Collomb, A Tejada, J.C.Joubert, *J.,PhysC.* 19(1986) 6605
6. D.B. Ghare, A.P.B. Sinha, *J.Phys Chem Solid* 29(1958) 885
7. Isalgue, A Laberta, J.Tejada, X Obradir. *Appl. Phys A* 39(1986) 221
8. S.S.Darokar, K.G.Rewatkar and D.K.Kulkarni *Mater Chem.Phys.* 56 (1998) 84-85
9. K. Haneda, M. Kojima, *J. Appl. Phys* 14.B(1973) 3760
10. Albense G, Carbulichio and Deril A *J.Phys Solid State: A* 23 (1974) 351
11. K. Haneda, H. Kojima. *Phys State Solid (A)* 6(1971) 256
12. J. Lipka, A. Gruskova, O. Orlicky, J. Siteck, M. Miglierini, R. Grone, M. Hud and Toth *Hyperfine Interaction* 59(1990) 381.
13. S.S. Darokar, K.G. Rewatkar & D.K. Kulkarni, *Indian J.Phys.* 74A (2) (2000) 155-157
14. Suresh. S. Darokar *et.al.*, *J. Adv. Appl. Sci. Res*, 2013, 4(1): 173-177
15. Z. Redrigue, Obradors X, Labrata A, Tejeja. J.Pernet M. M. Solid Paul and J.Tholente, *J. Phys Collog* 149 (1988) 119
16. E.J. Verway J.H, De-Bar.Pec.Trar. *Chem Pay Bull* 55 (1936) 531