

Some sulfated water soluble natural polymer (Carrageenans) compounds as corrosion inhibitors for dissolution of iron in hydrochloride acid solution

K.S. KHAIROU and I. ZAAFARANY

Chemistry Department, Faculty of Applied Sciences, Umm Al -Qura University,
Makkah Al Mukaramha P.O. Box - 118 (Saudi Arabia)

(Received: September 12, 2006)

ABSTRACT

The effect of some sulfated water soluble polymer (carrageenan) compounds on the corrosion behavior of iron electrode in 1M hydrochloric acid solution as corrosive medium has been investigated using galvanostatic polarization technique. Some corrosion parameters such as anodic and cathodic Tafel slope, corrosion potential, corrosion current density, surface coverage and inhibition efficiency was calculated. The polarization measurements indicated that the inhibitors are mixed type. The inhibition efficiency was found to increase with increasing concentration and number of sulfur atom per molecules. Inhibition was explained on basis of parallel adsorption of these compounds on the iron electrode. The adsorption process follows Langmuir adsorption isotherm.

Key words: Iron, corrosion inhibitors, adsorption, Carrageenans compounds

INTRODUCTION

The study of corrosion is of high practical and technological interest. Acids find applications in industrial acid cleaning, acid pickling, acid descaling and oil well acidizing. Inhibitors are commonly employed in these environments to minimize the base metal corrosion by the acids. The selection of appropriate inhibitors mainly depends on the type of acid, its concentration, temperature, velocity, presence of dissolved solids and the type of metallic materials involved. The important prerequisites for a compound to be an efficient inhibitor are: i) it should form a defect free, compact barrier film. ii) it should chemisorb on to the metal surface. iii) it should be polymeric polymerize in sites on the metal and iv) the barrier thus formed should increase the inner layer thickness.


Most of the well-known inhibitors used for

inhibition of iron in acidic medium are organic compounds containing nitrogen, sulphur and /or oxygen atoms¹⁻¹⁰. It has been observed that most of the organic inhibitors act by adsorption on the metal surface¹¹. This phenomenon is influenced by the nature and surface charge of metal, by the type of aggressive electrolyte and by the chemical structure of inhibitors.


The aim of the present work is to study the effect of these compounds of sulfated water soluble natural polymer (carrageenan) compounds as corrosion inhibitors on the corrosion of iron in 1M HCl using galvanostatic polarization technique.

Carrageenans compounds


Carrageenans are linear polymer of about 2500 galactose derivatives with regular but imprecise structure dependent on the source and extraction conditions. The structural unit of these compounds are as follows:

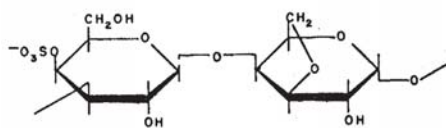

Compound (I) Carrageenan (Kappa)

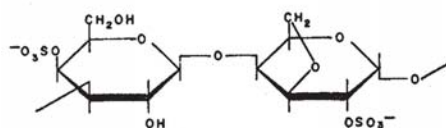

Compound (II) Carrageenan (Iota)

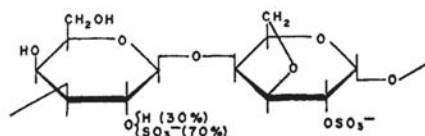

Compound (III) Carrageenan (Lambda)

EXPERIMENTAL

Iron electrode having the chemical composition (%): 0.052C, 0.189 Mn, 0.008P, 0.011 S, 0.011 Si, 0.012 Cr, 0.029Ni, 0.04 Cu, 0.039 Al and the remainder is Fe, provided by the "Saudi iron and steel company" was used in the present study. The bottom end of the rod specimen with a mean surface area of 1cm² was successively abraded with 1-,0- and 00- emery paper, degreased with acetone and dried between filter paper then immersed in 100 ml of the test solution.

Galvanostatic polarization measurements were carried out using Mensberg potentiostat/galvanostat PS6 with controlling software (PS remote) was used for accurate measurements of potential and current density. Three compartment cell with a saturated calomel reference electrode (SCE) and a platinum foil auxiliary electrode was used.

RESULTS AND DISCUSSION

Addition of different concentrations of carrageenans compounds on the galvanostatic polarization of iron electrode was studied in 1M HCl. Fig. 1 shows that the effect of compound III as a typical example. Similar curves were obtained for other compounds (not shown). From these curves

one can observe that at first transition region in which the potential increases (anodic polarization) or decreases (cathodic polarization) slowly with current density followed by a rapid linear increase of potential (Tafel region).

Transition region¹² which starts from the free corrosion potential and extends to the beginning of the Tafel region is characterized by the simultaneous occurrence of cathodic hydrogen evolution and anodic dissolution of metal. At the end of transition region there is a metal dissolution and the current becomes purely anodic (anodic polarization) or hydrogen evolution takes place with suppressing the metal dissolution and the current is purely cathodic (cathodic polarization).

The values of corrosion current density ($I_{corr.}$) was determined by the intersection of the extrapolated of the cathodic and anodic Tafel lines with the stationary corrosion potential ($E_{corr.}$). The percentage inhibition efficiency (I.E) was calculated using the following equation.

$$I.E. = \left(1 - \frac{I_{add}}{I_{free}}\right) 100 \quad \dots(1)$$

where, I_{add} and I_{free} are the corrosion current densities in the absence and presence of the inhibitors, respectively.

Table -1 shows the effect of inhibitor concentrations on the corrosion kinetic parameters such as anodic and cathodic Tafel slopes (β_a and β_c), $E_{corr.}$, $I_{corr.}$, surface coverage θ and I.E.

An inspection of the results obtained from Table -1 reveals that, the increasing in concentrations of the additives compounds show the following:

- i) The corrosion potential ($E_{corr.}$) is shifted to more positive values and the corrosion current density ($I_{corr.}$) decrease with increasing inhibitor concentration indicates the inhibiting effect of these compound.
- ii) The values of anodic and cathodic Tafel slopes (β_a and β_c) are approximately constant which suggest the simple blocking of the available surface area of the metal by the inhibitor molecules. In other words, the adsorbed inhibitor molecules decreases the

Table - 1: Corrosion parameters obtained from galvanostatic polarization technique of iron electrode in 1M HCl containing different concentrations of carrageenans compounds

	Inhibitor conc., ppm	I_{corr} , ($\mu A cm^{-2}$)	E_{corr} , mV(SEC)	β_a mV dec ⁻¹ mV dec ⁻¹	β_c	θ	I.E
Compound I	0.00	1.65	-530	163	-200	-	-
	100	0.755	-276	166	-197	0.755	54.24
	200	0.705	-278	154	-191	0.705	57.27
	300	0.656	-274	157	-189	0.656	60.24
	400	0.573	-270	166	-200	0.573	65.27
	500	0.468	-261	160	-203	0.468	71.64
Compound II	0.00	1.65	-530	163	-200	-	-
	100	0.672	-320	153	-191	0.593	59.27
	200	0.612	-305	147	-206	0.629	62.88
	300	0.572	-295	161	-216	0.653	65.33
	400	0.513	-282	154	-216	0.689	68.91
	500	0.435	-268	165	-207	0.736	73.64
Compound III	0.00	1.65	-530	163	-200	-	-
	100	0.606	-315	165	-206	0.633	63.27
	200	0.570	-306	158	-196	0.654	65.43
	300	0.524	-297	164	-215	0.682	68.24
	400	0.453	-281	156	-208	0.725	72.54
	500	0.342	-278	160	-212	0.793	79.27

surface area available for the both metal dissolution and hydrogen evolution reaction without affecting the reaction mechanism¹³. Therefore, it could be concluded that the carrageenans compounds affect on both anodic and cathodic reaction (i.e.) mixed inhibitors.

- iii) The values of IE was found to increase with increasing the inhibitor concentration. The inhibition achieved by these compounds decreases in the following order:


compound III > compound II > compound I

The inhibition effect of these compounds can be attributed to their parallel adsorption at the metal solution interface. The parallel adsorption is owing to the presence of one or more active centre for adsorption.

Adsorption isotherms

Carrageenan compounds inhibit the

corrosion process by the adsorption on metal surface. Theoretically, the adsorption process can be regarded as a single substitution an "x" number of water molecules adsorbed on the metal surface¹⁴ viz,



where x is known as the size ratio and simply equals the number of adsorbed water molecules replaced by a single inhibitor molecules. The adsorption depends on the structure of the inhibitor, the type of the metal and the nature of its surface, the nature of the corrosion medium and its pH value, the temperature and the electrochemical potential of the metal solution interface. Also, the adsorption provides information about the interaction among the adsorbed molecules themselves as well as their interaction with the metal surface. Actually an adsorbed molecules may make the surface more difficult or less difficult for another molecules to become attached to a neighboring site and

multilayer adsorption may take place. Finally, various surface sites could have varying degrees of activation. For these reasons a number of mathematical adsorption isotherm expression have been developed to take into consideration some of non-ideal effects.

The resulted inhibitive action of polymer compounds due to adsorption of its compounds on the iron surface making a barrier for charge and mass transfer between the metal and corrosive environment. As the concentration of polymer compounds increases, the fraction of iron surface covered by adsorbed molecules (θ) increases resulting in higher inhibition efficiency.

The degree of surface coverage (θ) was calculated using the following equation :

$$\theta = 1 - \frac{I_{\text{add}}}{I_{\text{free}}} \quad \dots(3)$$

where I_{free} and I_{add} are the corrosion current densities in the absence and presence of the additive compounds, respectively. The value of θ are reported in Table -1. The degree of surface

coverage θ was found to increase with increasing the concentration of additives.

Attempts were made to fit θ values to various isotherms e.g. (Frumkin, Temkin, Freundlich and Langmuir). The best fit was obtained with Langmuir isotherm according to the following equation.

$$\frac{\theta}{1 - \theta} = KC \quad \dots(4)$$

and rearranging it gives:

$$\frac{C}{\theta} = \frac{1}{K} + C \quad \dots(5)$$

where (C) is the concentration of additive is the equilibrium constant of adsorption.

The plot of $\frac{C}{\theta}$ against C gives a straight lines of intercept $\frac{1}{K}$. The plots are shown for

polymer compounds additives in Figure (2). The resulted straight lines from the above relation have almost the unit slopes. This indicates that, the adsorption of polymer compounds on the iron

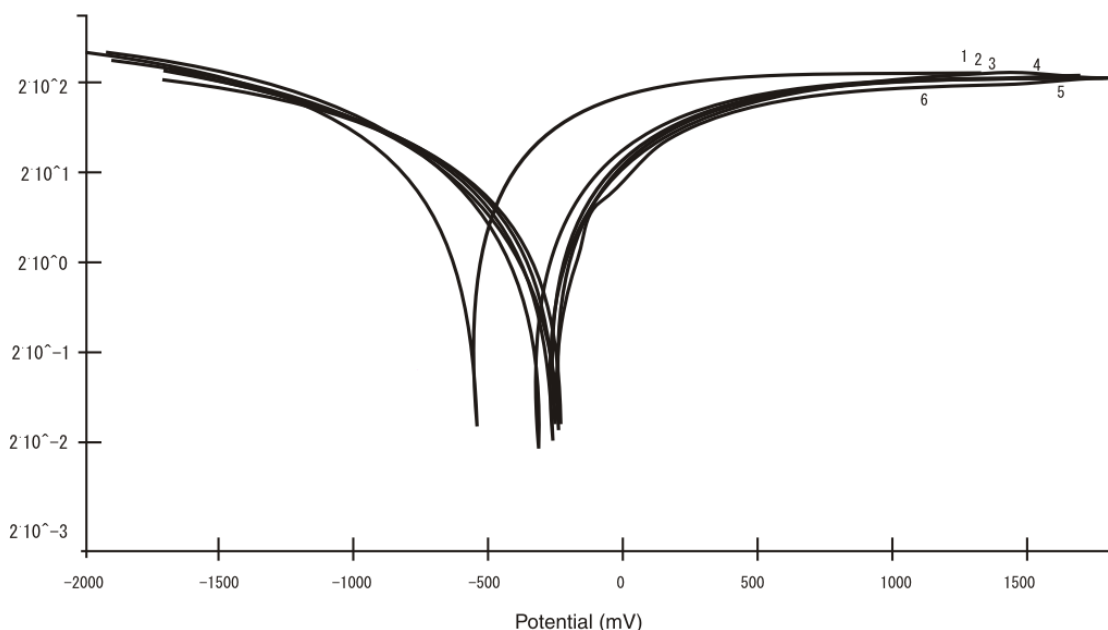


Fig. - 1: Galvanostatic polarization curves for iron electrode in 1M HCl in absence and presence of different concentration of compound III
 1) 0.00ppm 2) 100 ppm 3) 200 ppm 4) 300 ppm 5) 400 ppm 6) 500 ppm.

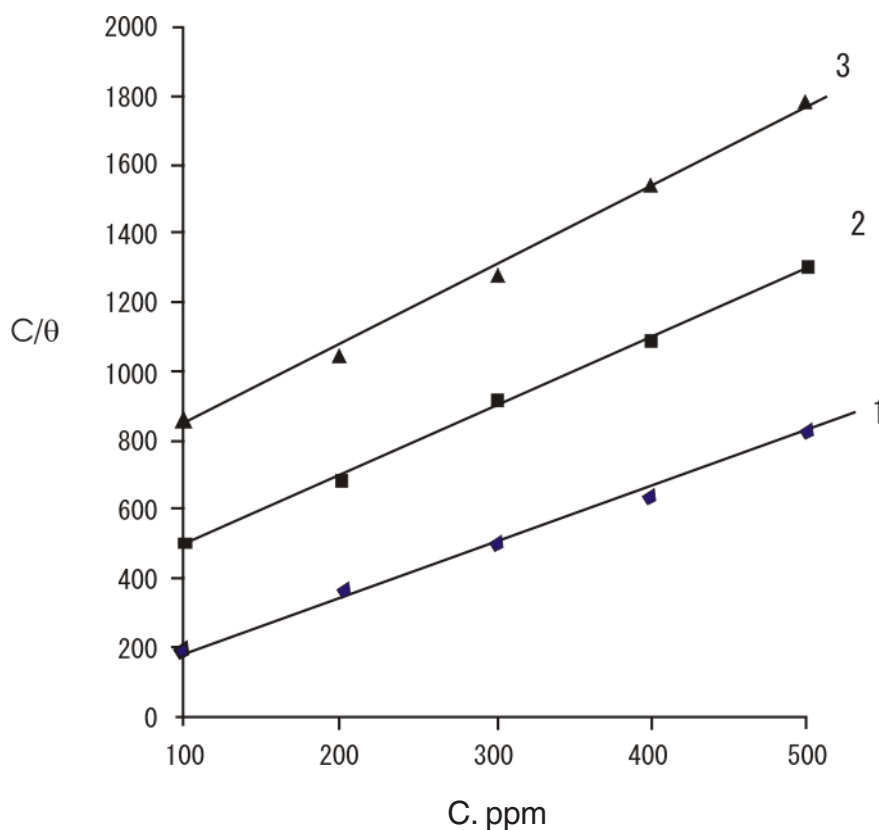


Fig. - 2: Langmuir adsorption isotherm
1) compound I 2) compound II 3) compound III

surface follows Langmuir adsorption isotherm and consequently, there is no interaction between the molecules adsorbed at the iron surface.

The equilibrium constant of adsorption (K_a) is related to the standard free energy of adsorption (ΔG^*_{ads}) by the relation^{15,16}.

$$K_a = \frac{1}{55.5} \exp \left[\frac{-\Delta G^*_{ads}}{RT} \right] \quad \dots(6)$$

where R is universal gas constant, the value 55.5 is the concentration of water in the solution in mole.

The values of K_a and ΔG^*_{ads} of the inhibitors adsorbed on the iron surface were calculated and listed in Table -2.

Table - 2: The equilibrium constant of adsorption and the standard free energy of adsorption of the carrageenas compounds on the surface of iron at 25°C

Inhibitors	K_a	ΔG^*_{ads} KJ mole ⁻¹
Compound I	5.57×10^{-3}	-2.939
Compound II	2.08×10^{-3}	-5.445
Compound III	1.54×10^{-3}	-6.092

The standard free energy of adsorption is associated with water adsorption /desorption equilibrium which forms an important part in the overall free energy change of adsorption. It is clear that ΔG^*_{ads} increases with increasing the size of molecules¹³. The negative values of ΔG^*_{ads} obtained here indicated that the adsorption process of these compounds on the iron surface is spontaneous one.

Conclusions

- 1- Carrageenans compounds act as an inhibitor for corrosion of iron in 1M HCl solution.
- 2- The inhibition efficiency increases with the increasing the inhibitor concentrations.
- 3- The inhibition process is due to the adsorption of the inhibitor molecule on the iron surface.
- 4- The adsorption of carrageenans compounds on the iron surface follows Langmuir adsorption isotherm.

REFERENCES

1. Abd El-Maksoud, S. A.: *Corros. Sci.*, **44**, 803 (2002).
2. Abdel Rehim, S.S., Khaled, K. F. and Abd El-Shafi, N.S.: *Electrochim Acta*, **51**(16), 3269 (2006).
3. Abd El. Maksoud, S.A.: *Appl. Surf. Sci.*, **206**, 129 (2003).
4. Jeyaprabha, C., Sathiyarayanan, S. and Venkatachari, G.: *Electrochim Acta*, **51** (19), 4080 (2006).
5. Chetouani, A., Hanrmouti, B., Benhadda, T. and Daoudi, M., *Appl. Surf. Sci.*, **249** (1-4), 375 (2005).
6. Khaled, K.F.: *Appl. Surf. Sci.*, **230**, 307 (2004).
7. Emergöl, K.C. and Atako, O.: *Materials Chem. and Phys.*, **82** (2-3), 373 (2004).
8. Khaled. K. F.: *Electrochim Acta*, **48** (17), 2493 (2003).
9. Chebabe, D., Ait Chikh, Z., Hajjaji, N., Shiri, A. and Zucchi, F.: *Corros. Sci.*, **45** (2) , 309 (2003).
10. Abd El-Maksoud, S. A. : *Corros. Sci.*, **44** (4) 803 (2002).
11. Abdallah, M.: *Materials Chem. and Phys.*, **82**, 786 (2003).
12. Epelbion, I., Morel, P. and Tokenout, H.: *J. Electrochem. Soc.*, **118**, 1282 (1971).
13. Blomgern, E., Bockris, J.O.M. and Jesech, C.: *J. Phys. Chem.*, **65**, 200 (1961).
14. Lu, B.T., Chen, Z.K., Luo, J.L., Patchett, B.M. and Xu, Z.H.: *Electrochim Acta*, **50**(6)139 (2005).
15. Kliskic, M., Radosevic, J. and Gndic: *J. Appl. Electrochem.* **27**, 947 (1997).
16. Abdallah, M.: *Bull of Electrochem.* **16** (6), 258 (2000).